

Journal of Materials Science

Laser powder bed fusion of WC-reinforced Hastelloy-X composite: microstructure and mechanical properties --Manuscript Draft--

Manuscript Number:	JMSC-D-20-04977R3
Full Title:	Laser powder bed fusion of WC-reinforced Hastelloy-X composite: microstructure and mechanical properties
Article Type:	Manuscript (Regular Article)
Keywords:	Additive manufacturing; Laser powder bed fusion; Ceramic particles; Composites; mechanical performance; Cracking
Corresponding Author:	Quanquan Han, PhD Shandong University Jinan, CHINA
Corresponding Author Secondary Information:	
Corresponding Author's Institution:	Shandong University
Corresponding Author's Secondary Institution:	
First Author:	Quanquan Han, PhD
First Author Secondary Information:	
Order of Authors:	Quanquan Han, PhD Yuchen Gu Heng Gu Yingyue Yin Jun Song Zhenhua Zhang Shwe Soe
Order of Authors Secondary Information:	
Abstract:	<p>Nickel-based superalloys such as Hastelloy X (HX) are widely used in gas turbine engines for their exceptional oxidation resistance and high-temperature strength. The addition of ceramic reinforcement further enhances these superalloys' mechanical performance and high-temperature properties. For this reason, this paper investigates the microstructure and mechanical property of laser powder bed fusion (LPBF) additively manufactured HX-1 wt.% WC (tungsten carbide) composite specimens. The results demonstrate that the LPBF-fabricated composite was observed to have several pores and microcracks, while only pores were detected in the as-fabricated pure HX. Compared to the fabricated pure HX, the tensile yield strength of such HX composite parts was increased by 13% without undue sacrifices to ductility, suggesting that the very limited number of microcracks were not sufficient to degrade the mechanical performance. The significantly increased dislocations were considered to be the primary contributor for the mechanical performance enhancement in the LPBF-fabricated composite material. The findings offer a promising pathway to employ LPBF process to fabricate advanced microcrack-free composites with high-strength through a careful selection of ceramic reinforcement materials.</p>
Funding Information:	

Cover letter

Dear Editors,

I am pleased to offer our manuscript entitled 'Laser powder bed fusion of WC-reinforced Hastelloy-X composite: microstructure and mechanical properties'. I hope that you will find it of sufficient quality and interest for the readership of the journal.

The significance of this research is in the study of the effects of WC (tungsten carbide) reinforcement on the microstructure and mechanical properties of laser powder bed fusion (LPBF) additively manufactured HX–1 wt.% WC composite specimens. The results demonstrate that the LPBF-fabricated composite was observed to have several pores and microcracks, while only pores were detected in the as-fabricated pure HX. Compared to the fabricated pure HX, the tensile yield strength of such HX composite parts was increased by 13% without undue sacrifices to ductility. The findings offer a promising pathway to employ LPBF process to fabricate advanced microcrack-free composites with high-strength through a careful selection of ceramic reinforcement materials.

I confirm that the work submitted is original and has not been published before; it is not under consideration for publication anywhere else. Please be advised that colour is to be used in the electronic version only.

Corresponding author:

Quanquan Han, hanguanquan@sdu.edu.cn, School of Mechanical Engineering, Shandong University, Jinan, 250061, China

Best regards,

Quanquan Han

School of Mechanical Engineering, Shandong University, China

School of Engineering, Cardiff University, UK

Response to reviewers

Dear Editor,

The authors wish to thank the reviewers for their constructive and valuable comments, which significantly improve the manuscript. We have revised carefully our manuscript “**Laser powder bed fusion of WC-reinforced Hastelloy-X composite: microstructure and mechanical properties**” and addressed all comments. Please find the response to the reviewers’ comments below.

Yours sincerely,

Quanquan Han

Professor of Additive Manufacturing, School of Mechanical Engineering

Shandong University, China

The authors wish to thank the Reviewer #1 for their constructive and valuable comments.

Response to Reviewer #1	
Comments	Response
1. EDX spectrum: Still very hard to identify peaks, and other peaks are not labelled.	The authors much appreciate the reviewer's comment and his/her dedication to improve our paper, thanks again. The EDX spectrum has been replaced by a new measured one in the revised Fig. 3d.
2. EBSD: Impossible to say there is not texture just from one IPF map in each case. Further, it is still unclear if the IPF colour refers to orientations in the build direction or a transverse direction.	<p>The authors truly appreciate the reviewer's valuable comment and we do apologise for the misunderstanding about this comment. The IPF colour code refers to the orientation in the build direction in this paper; the coordinate system has been added in the revised Fig. 7a and hope it makes sense this time. Also, the statement about the texture has been modified in the revised manuscript (section 3.2, the second last paragraph, highlighted in red).</p> <p>Again, the authors would like to appreciate the reviewer's careful and rigorous review to this manuscript, which significantly improves this work and the authors do learn a lot from the valuable comments.</p>

[Click here to view linked References](#)

Laser powder bed fusion of WC-reinforced Hastelloy-X composite: microstructure and mechanical properties

Quanquan Han^{a,b*}, Yuchen Gu^c, Heng Gu^d, Yingyue Yin^{a,b}, Jun Song^e, Zhenhua Zhang^{a,b}, Shwe Soe^f

^aKey Laboratory of High Efficiency and Clean Mechanical Manufacture of Ministry of Education, Center for Additive Manufacturing, School of Mechanical Engineering, Shandong University, Jinan, 250061, China

^bKey National Demonstration Center for Experimental Mechanical Engineering Education, Shandong University, Jinan, 250061, China

^cCollege of Engineering, Swansea University, Swansea, SA1 8EN, UK

^dCardiff School of Engineering, Cardiff University, Cardiff, CF24 3AA, UK

^eCollege of Mechanical Engineering, Chongqing University, China

^fDepartment of Engineering Design and Mathematics, University of the West of England, Bristol, BS16 1QY, UK

Corresponding author:

Quanquan Han: Hanquanquan@sdu.edu.cn, Tel: +86 18866805250.

Abstract

Nickel-based superalloys such as Hastelloy X (HX) are widely used in gas turbine engines for their exceptional oxidation resistance and high-temperature strength. The addition of ceramic reinforcement further enhances these superalloys' mechanical performance and high-temperature properties. For this reason, this paper investigates the microstructure and mechanical property of laser powder bed fusion (LPBF) additively manufactured HX-1 wt.% WC (tungsten carbide) composite specimens. The results demonstrate that the LPBF-fabricated composite was observed to have several pores and microcracks, while only pores were detected in the as-fabricated pure HX. Compared to the fabricated pure HX, the tensile yield strength of such HX composite parts was increased by 13% without undue sacrifices to ductility, suggesting that the very limited number of microcracks were not sufficient to degrade the mechanical performance. The significantly increased dislocations were considered to be the primary contributor for the mechanical performance enhancement in the LPBF-fabricated composite material. The findings offer a promising pathway to employ

1 LPBF process to fabricate advanced microcrack-free composites with high-strength
2 through a careful selection of ceramic reinforcement materials.
3

4 **Keywords:** Additive manufacturing; Laser powder bed fusion; Ceramic particles;
5 Composites; Mechanical performance; Cracking
6
7

8 9 **1. Introduction**

10
11
12 Laser powder bed fusion (LPBF) is an additive manufacturing (AM) process in which
13 metallic powder is selectively melted layer by layer using a high-power laser source [1]
14 [2]. Nickel-based superalloys are widely used in gas turbine engine components due
15 to these materials' unique combination of oxidation resistance, formability and
16 mechanical properties in the temperature range of 540–1000 °C [3][4]. The benefits of
17 using Hastelloy-X (HX) alloy over other nickel-based superalloys include superior high-
18 temperature strength, better oxidation resistance and stress-corrosion cracking
19 resistance. For instance, compared to Inconel 718 and Inconel 625, HX alloy is
20 resistant to stress-strain cracking in petrochemical applications and offers good
21 ductility, even at temperatures as high as 1200 °C [5]. The inclusion of molybdenum
22 enables HX harder, stronger at high temperatures, and also makes it great for welding
23 applications. Because of these reasons, HX alloy is widely used in gas turbine engines
24 for combustion zone components, such as transition ducts, combustor cans and flame
25 holders. Because of the capability and flexibility of the LPBF process, in which metallic
26 components with complex geometries can be rapidly fabricated, the LPBF of nickel-
27 based superalloys has recently attracted increased attention as a promising
28 technology for the manufacture of complex structural components for the gas turbine
29 engine sector [6][7].
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44

45 Metal matrix composites (MMCs) exhibit the advantages of both matrix materials
46 and reinforcement phases and are usable in various applications in the aerospace,
47 defence and automotive domains [8][9]. Thus, the LPBF of MMCs has also received
48 growing interest from both the academic and engineering communities. As a result, a
49 wide range of reinforcement particles such as Al₂O₃, TiC, SiC, WC and TiB₂ have been
50 successfully employed in the LPBF of MMCs [10][11][12][13].
51
52
53
54
55
56

57 To date, several studies have focussed on combining the LPBF of nickel-based
58 superalloys and MMC philosophy to additively manufacture nickel-based composites.
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

However, the matrix materials employed in these studies mainly include Inconel 718 and Inconel 625. For instance, Gu et al. [14] investigated nano-TiC-reinforced Inconel 718 composites and found that refined near-spherical TiC reinforcements were evenly distributed in the matrix after the LPBF process, and much higher nanohardness values and lower wear rates could be obtained compared to the un-reinforced Inconel 718 components. Zhang et al. [15] studied the anisotropic corrosion resistance of TiC reinforced Inconel 718 composites fabricated by LPBF. They have found that the XZ-plane (parallel to the build direction) exhibited a weak anti-corrosion property because of the inhomogeneous microstructures, while the XY-plane (perpendicular to the build direction) was more prone to corrosion due to the irregular pores and clustered ring-like structures. Wang et al. [16] investigated the effects of carbon nanotube reinforcements on the LPBF-fabricated Inconel 625 composites. They have demonstrated that the composite exhibited a significant improvement in tensile strength with less elongation, this is because the composite offered a slightly faster cooling rate compared to the pure alloy. Rong et al. [17] investigated the gradient interface and wear performance of LPBF-fabricated Inconel 718-WC composite. Their findings revealed that the wear mechanism changed from abrasive wear to adhesive wear when the composite was subjected to dry sliding wear test. Nguyen et al. [18] studied the microstructure and mechanical properties of Inconel 718-WC composite fabricated by the LPBF process, with the size of the WC particles varying from 15 μm to 53 μm . They found that the WC particles hindered grain growth in the solidification stage and that the intermediate layer and strong bonding between WC particles and the matrix resulted in significant improvement in both microhardness and tensile strength. Thus, there is a scope to conduct similar research investigations but in the context of HX to study whether HX composites built with the LPBF could also exhibit similar improvements.

Previous studies have reported that the strengthening effect improves with decreases in the size of the reinforcement particles [19]. However, when this size reaches the sub-micrometre and nano regions, the high surface-area-to-volume ratio, along with the strong van der Waals force, together enable the reinforcements to agglomerate and form clusters. In turn, this represents a challenge for dispersing uniformly the sub-micrometre reinforcement particles amongst the metallic powder. One common method for dispersing such sub-micrometre reinforcement particles is

1 the high-energy ball-milling process, in which a certain number of very hard milling
2 balls are used to disperse the mixed powders for a few hours [20][21]. The high energy
3 that is generated during the ball-milling process, however, can damage the crystal
4 structure of the metallic powder in addition to the chemical contamination that
5 generally takes place after a long milling time.
6
7
8

9 In this context, the aim of this study is to synthesise HX with 1 wt.% sub-micrometre
10 WC feedstock using a dual asymmetric high-speed mixing technique to uniformly
11 disperse the WC reinforcement without damaging the crystal structure of the HX. The
12 WC sub-micrometre ceramic particles were selected because WC could retain its
13 room temperature hardness up to 1400 °C; it also exhibits excellent wear resistance,
14 corrosion resistance and chemical stability with no phase changes during heating and
15 cooling [22][23][24]. The addition of WC particles is expected to result in the
16 enhancement in tensile strength and also improve the composite's high-temperature
17 properties, which offers great potential for advanced HX composite in the applications
18 of gas turbine engines. Another novelty of this work is its exploration on the
19 microcracking formation mechanism for LPBF-fabricated composites.
20
21
22
23
24
25
26
27
28
29

30 **2. Materials and experimental procedure**

31 *2.1. Feedstock powder materials*

32
33 The commercial HX powder used in this study was provided by Sandvik Osprey
34 (Neath, UK) through gas atomisation with nitrogen. Using laser diffraction analysis, the
35 HX powder was measured to have an average particle size of 34 µm, with a spherical
36 morphology (Fig. 1a/c). The alloying composition (wt.%) of the HX powder is shown in
37 Table 1.
38
39
40
41
42
43
44

45 **Table 1.**

46 Alloying composition of the HX powder.

47 Element	Cr	Fe	Mo	Co	W	Si	Ti	Al	C	Ni
48 wt. %	21.4	18.6	9	1.49	0.58	0.15	0.01	0.04	0.014	Bal.

49
50
51 The sub-micrometre WC reinforcement particles (150–200 nm) were acquired from
52 Sigma Aldrich (UK). As mentioned earlier, due to the high surface-area to volume ratio,
53 such particles tend to agglomerate to form clusters (Fig. 1b).
54
55
56
57
58
59
60
61
62
63
64
65

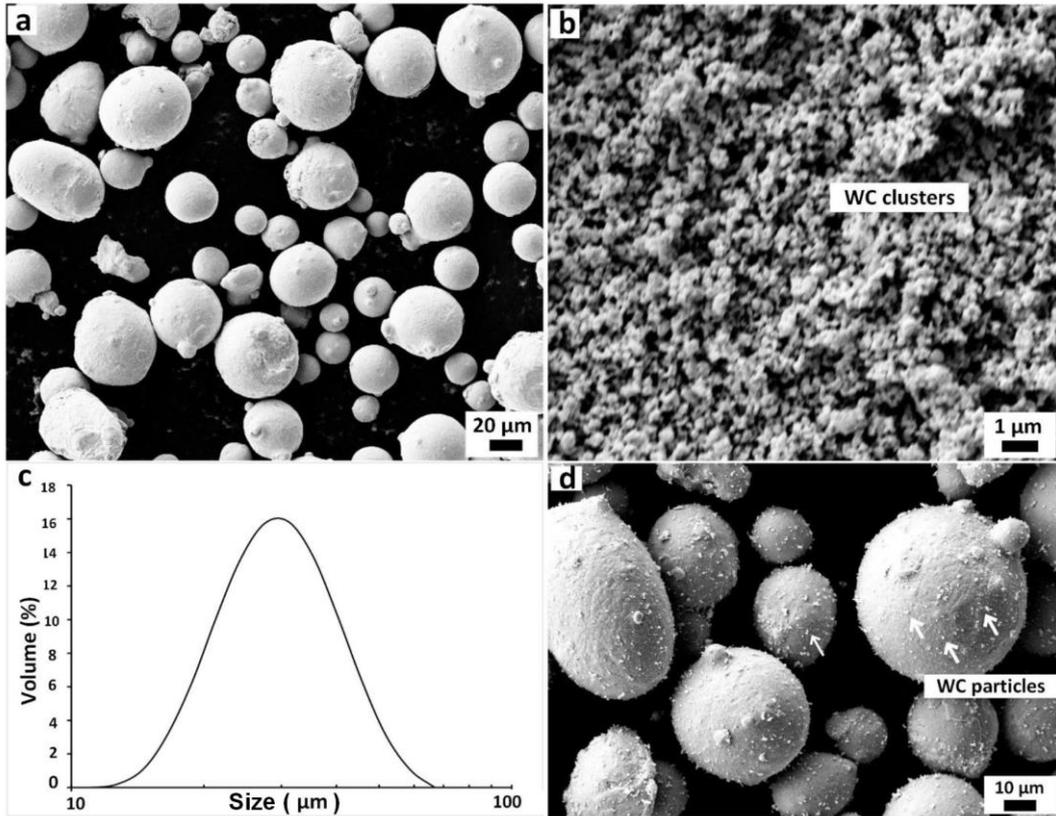


Fig. 1. Feedstock powder materials used in this study: (a) original Hastelloy X powder; (b) agglomerated WC particles; (c) particle size distribution of Hastelloy X powder; (d) high-speed mixed Hastelloy X with 1 wt.% WC composite powder.

A commercial high-speed mixer (SpeedMixer, DAC 800.1 FVZ, Hauschild, Germany) with a maximum speed of 2,000 rpm was used to synthesise the HX–1 wt.% WC composite feedstock. The mixer employs a dual asymmetric technology to disperse the WC particles. The mixing parameters include a mixing speed of 1,200 rpm, with 5 minutes of mixing time. Fig. 1d shows the synthesised HX-WC composite feedstock. The WC clusters were successfully broken up and dispersed on the surface of the HX powder, which suggests that the high-speed mixing process separated the clusters by overcoming the van der Waals adhesive force.

2.2. Specimens and selective laser melting

A Renishaw AM250 (Renishaw Plc, UK) system was employed in this study to fabricate both the tensile and lattice specimens. Based on preliminary experiments, the optimum primary parameters for building the HX and HX-WC composite samples were determined to be as follows: laser power = 200 W; layer thickness = 40 μm ; hatch spacing = 100 μm ; scanning speed = 600 mm/s [25]. The rotation angle was set to 67° between any two adjacent layers to minimise the porosity of the fabricated samples

(Fig. 2a). The dimensions of the tensile specimens were determined based on the ASTM-E8/E8M-13a guidelines (Fig. 2b). The tensile specimens are used to examine the effects of WC reinforcement on the mechanical properties of the LPBF-fabricated composites. It should be noted that the laser beam is running in pulsed mode with a point distance of 60 μm to manufacture samples rather than in continuous mode (Fig. 2c).

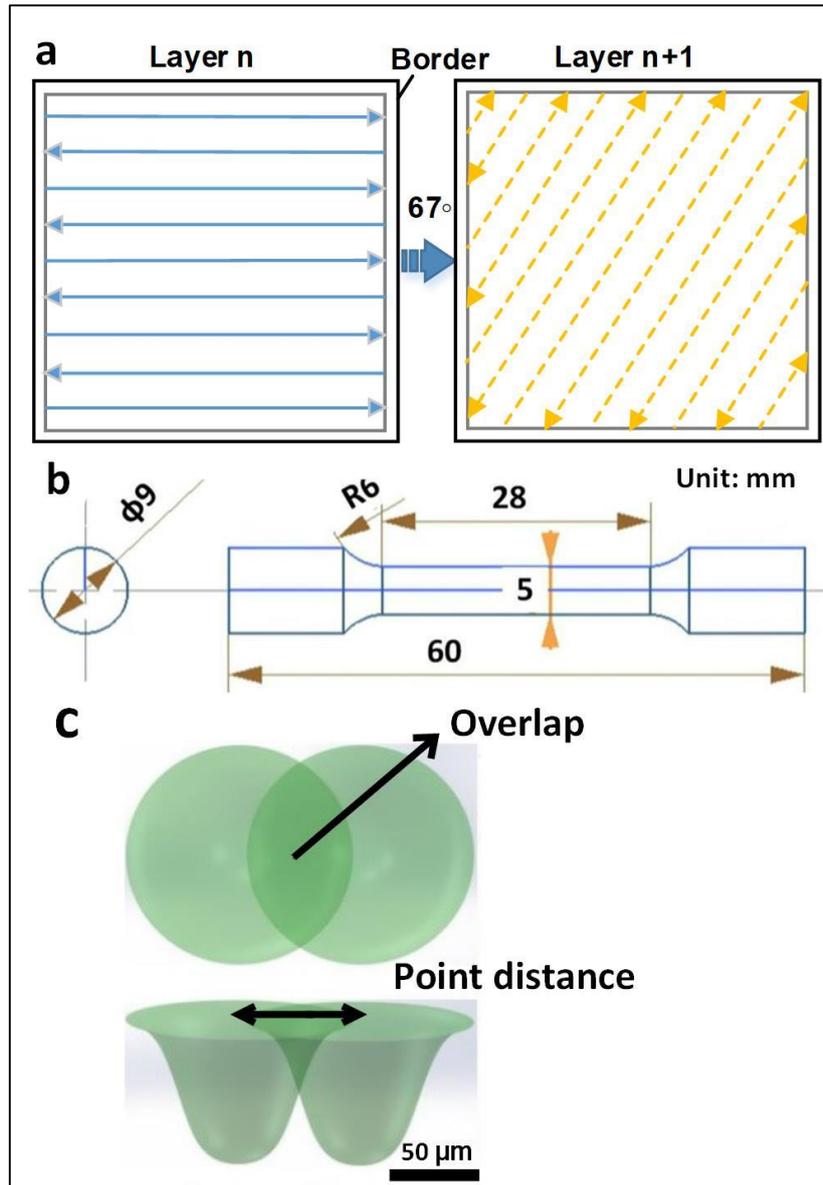


Fig. 2. Schematic of the employed laser melting strategy and samples: (a) the laser melting strategy; (b) the dimensions of the tensile specimens; (c) the working mode of the employed pulsed laser beam.

2.3. Material characterisation

Both pure HX and HX-WC composite samples were vertically sectioned, ground and polished prior to inspection via optical microscopy (OM) and scanning electron

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

microscopy (SEM) similarly to the procedure described in [26]. The polished samples were electrochemically etched using oxalic acid to reveal the microstructure and molten pools that formed. Backscattered electron (BSD) SEM mode was used to investigate the distribution of the WC particles and energy-dispersive X-ray spectroscopy (EDS) mapping was employed to examine the chemical composition of the as-fabricated specimens. Electron backscatter diffraction (EBSD) analysis was performed using a high resolution Jeol 7800F FEG-SEM equipped with an Oxford Instruments AZtec EBSD system, to study the microstructure evolution and grain crystallographic orientations. Uniaxial tensile testing was performed using a Zwick/Roell tester (maximum load of 100 kN) with a strain rate of $1.33 \times 10^{-3} \text{ s}^{-1}$ at room temperature. The engineering tensile stress-strain curves were then obtained on the basis of two specimens for each material.

3. Results

3.1. Surface finish

Fig. 3 shows the surface finish of the as-fabricated pure HX and HX-WC composite samples. Both balling and spattering surface defects were observed on the top surface of the two samples (Fig. 3a–b). The balling defects were more likely to have been formed in the ‘valley zone’, where two adjacent tracks overlap. These defects typically occur because, during the solidification stage, the thermal gradient and surface tension gradient enabled the formation of unstable molten tracks. As a result, the molten materials tend to reduce the surface energy and to form balls on the track edge [27]. Balling is detrimental to surface quality and can be controlled by optimising the process parameters.

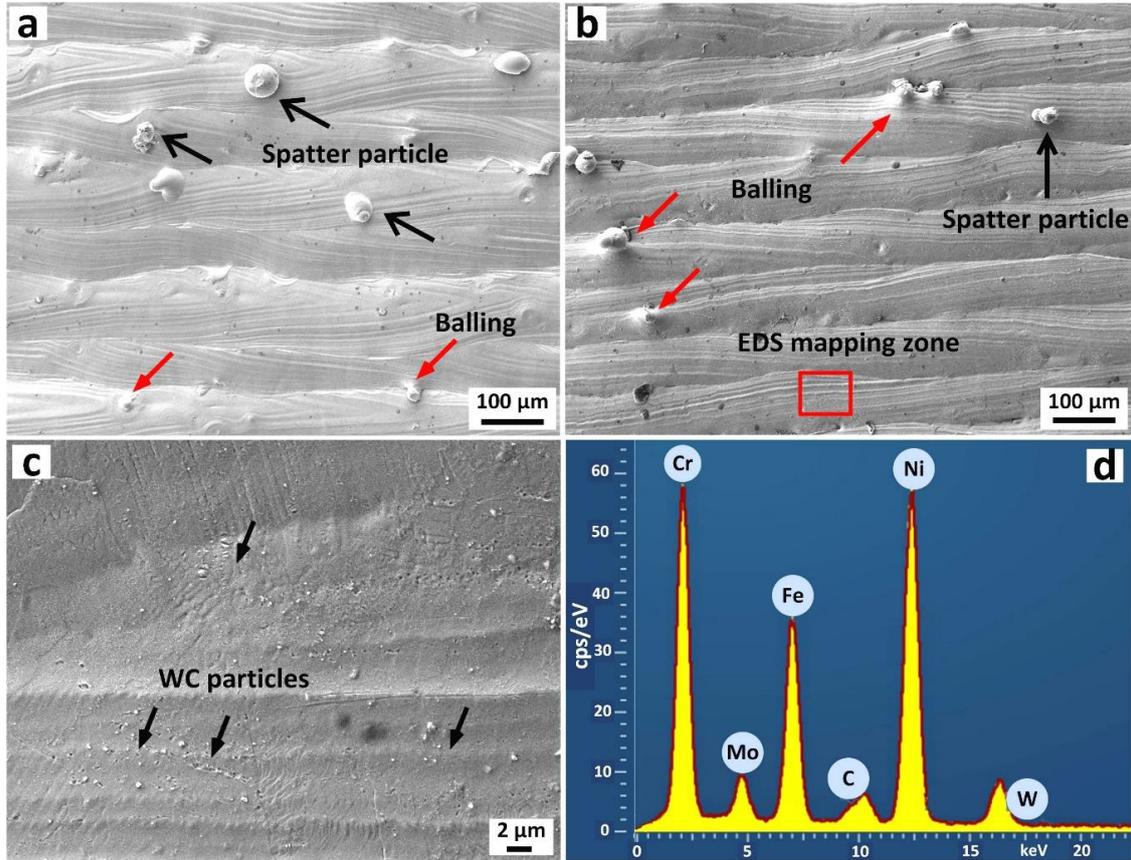


Fig. 3. Surface finish of as-fabricated samples: (a) pure HX; (b) HX-1 wt.% WC composite; (c)-(d) EDS spectrum taken from the zone in (b) showing the WC particles on the sample surface.

In addition to balling defects, spattered particles were also observed on the top surface and were distributed more randomly [28]. These spattered particles may be classified into two types based on particle size: (1) large spatters with sizes greater than 10 μm, and (2) small spatters below 10 μm. The mechanism of spatter formation has already been investigated in several previous reports (see [29] [30] [31]) and will not be discussed in the present work. Fig. 3c and d show the EDS spectrum taken from the measured area referenced in Fig. 3b. In addition to peaks of the primary alloying elements (i.e. Fe, Ni and Mo), strong W peaks were also detected, implying the existence of WC particles on the surface of the HX-WC composite samples. The Marangoni convection drove the migration of WC particles in molten pools; the WC particles were dispersed and the majority stayed inside the molten pools, while the rest were pushed out and stayed on the surface after the solidification. Another factors that caused the WC particles motion to the surface zone include the recoil pressure induced by the evaporation of the boiled molten HX material [32] and the poor wettability of WC ceramic particles so that some WC particles remained on the surface

1 of the melt pools after rapid solidification. It should be noted that the poor wetting
2 between the WC particles and the molten HX material may result in interfacial defects
3 in the fabricated composite components.
4

5 6 *3.2. Microstructure analysis*

7
8 Fig. 4 shows the microstructure of the vertical sections (parallel to the build direction)
9 for both pure HX and HX-WC composite under optical microscopy (OM). Both samples
10 were measured to have a relative density greater than 99.3%, on the basis of the
11 Archimedes method. A few open pores smaller than 40 μm were observed on the pure
12 HX (Fig. 4a), while several extra microcracks were found to have formed on the
13 composite sample (Fig. 4c). The factors that could cause porosity include a lack of
14 fusion [10], the inclusion of oxide [33], internal gas porosity from the feedstock [34]
15 and gas entrapment during laser melting [35]. When the molten pools for the etched
16 samples were compared, pure HX visibly exhibited much narrower and deeper molten
17 pools compared to the composite, even though the samples were manufactured under
18 the same conditions (Fig. 4b and d). This outcome may be explained by the addition
19 of 1 wt.% sub-micrometre WC particles, which altered the material thermal conductivity
20 and regulated laser absorption. Many studies have demonstrated that the composite
21 powder feedstock witnesses a significant increase in laser absorption due to the
22 increase in surface roughness [36][37][38], while the effective thermal conductivity
23 reduces because of the interfacial thermal resistance compared to the matrix alloys
24 [39][40]. The changes in thermo-physical properties could further affect the size of
25 melted zone and heat affected zone. In addition, the melting dynamics is also altered
26 due to the changes in viscosity and weldability after the addition of WC particles, which
27 also changed the molten pool shapes of the as-fabricated composite. In addition to the
28 open pores that were observed, several microcracks along the build direction (referred
29 to and annotated as BD in Fig. 4 and following figures) were also detected in the
30 composite specimen (Fig. 4d). The possible mechanisms for microcrack formation will
31 be discussed in the next subsection.
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

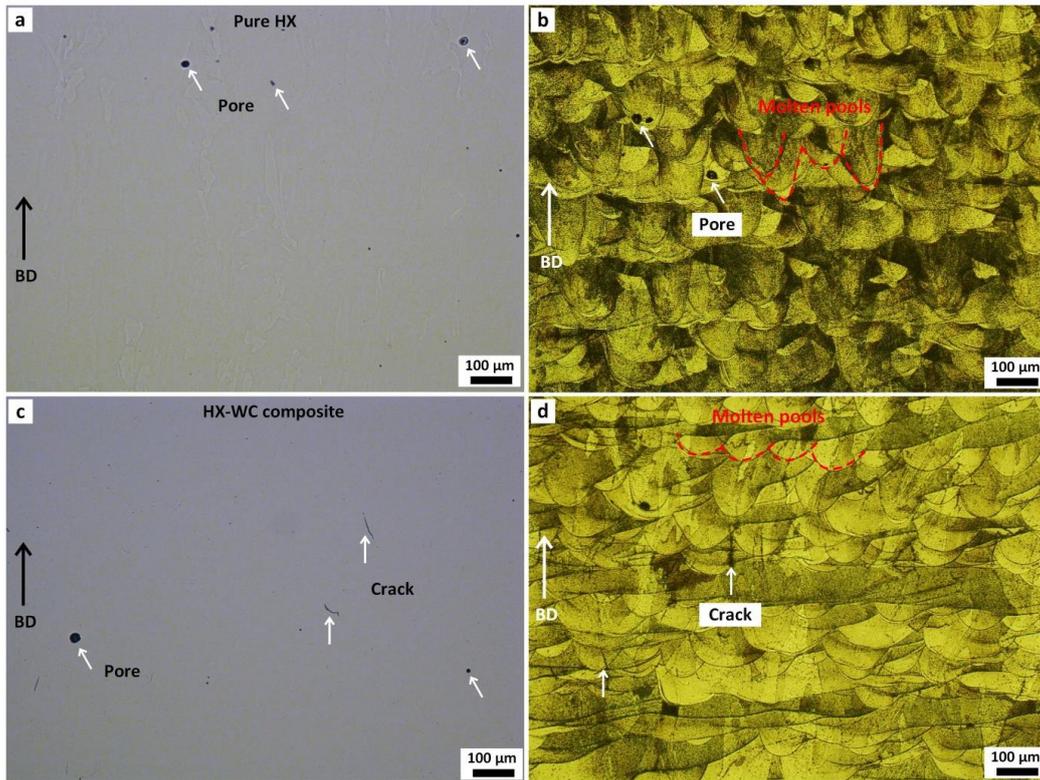


Fig. 4. OM images showing the microstructure of vertical sections of (a)-(b) as-fabricated pure HX; (c)-(d) as-fabricated composite specimen.

Fig. 5 shows the microstructure of the two samples under SEM examination. For both samples, fine cellular and columnar solidification structures were observed to have formed. The size of cellular structures and grains orientation are known to be linked to solidification conditions such as cooling rate and thermal gradient [41] [42]. One should note that the columnar grains grew across the fusion boundaries (Fig. 5a), indicating that the grains grew along the positive thermal gradient. The dendritic spacing was not found to differ significantly between the pure HX and composite specimens. The microcracks that formed in the composite were measured to vary from several to a hundred micrometres, which implies that the cracks propagated to a few layers along the build direction. In addition, the microcracks tended to form at the grain boundaries, which suggests that they were intergranular cracks.

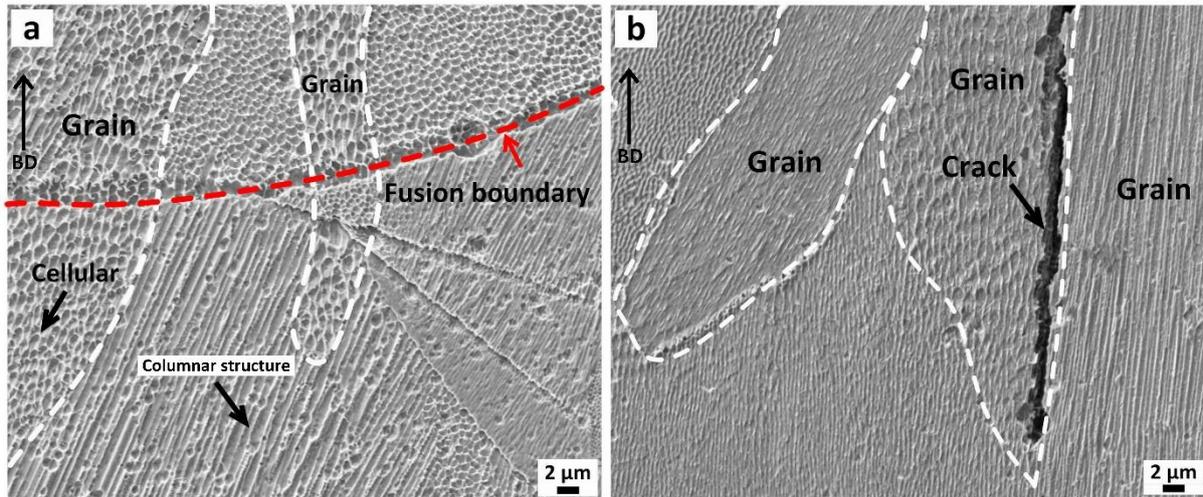


Fig. 5. SEM images showing the microstructure of as-fabricated samples: (a) pure HX with typical solidification structure formed; (b) microcrack formed in the composite specimen.

It should be noted that microcracks were not detected in the fabricated pure HX alloy, but were observed in the composite samples, suggesting that the added sub-micrometre WC particles enabled the grain boundaries more susceptible to hot cracking. Considering the coefficient of thermal expansion (CTE) of HX alloy and WC ceramic material, which are $15 \mu\text{m}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$ and $5.5 \mu\text{m}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$, respectively, the difference in CTE thus was a possible contributor to the microcracks formation. Furthermore, the microcracks could be easily generated if the sub-micrometre WC particles agglomerated at the grain boundaries during the rapid solidification process.

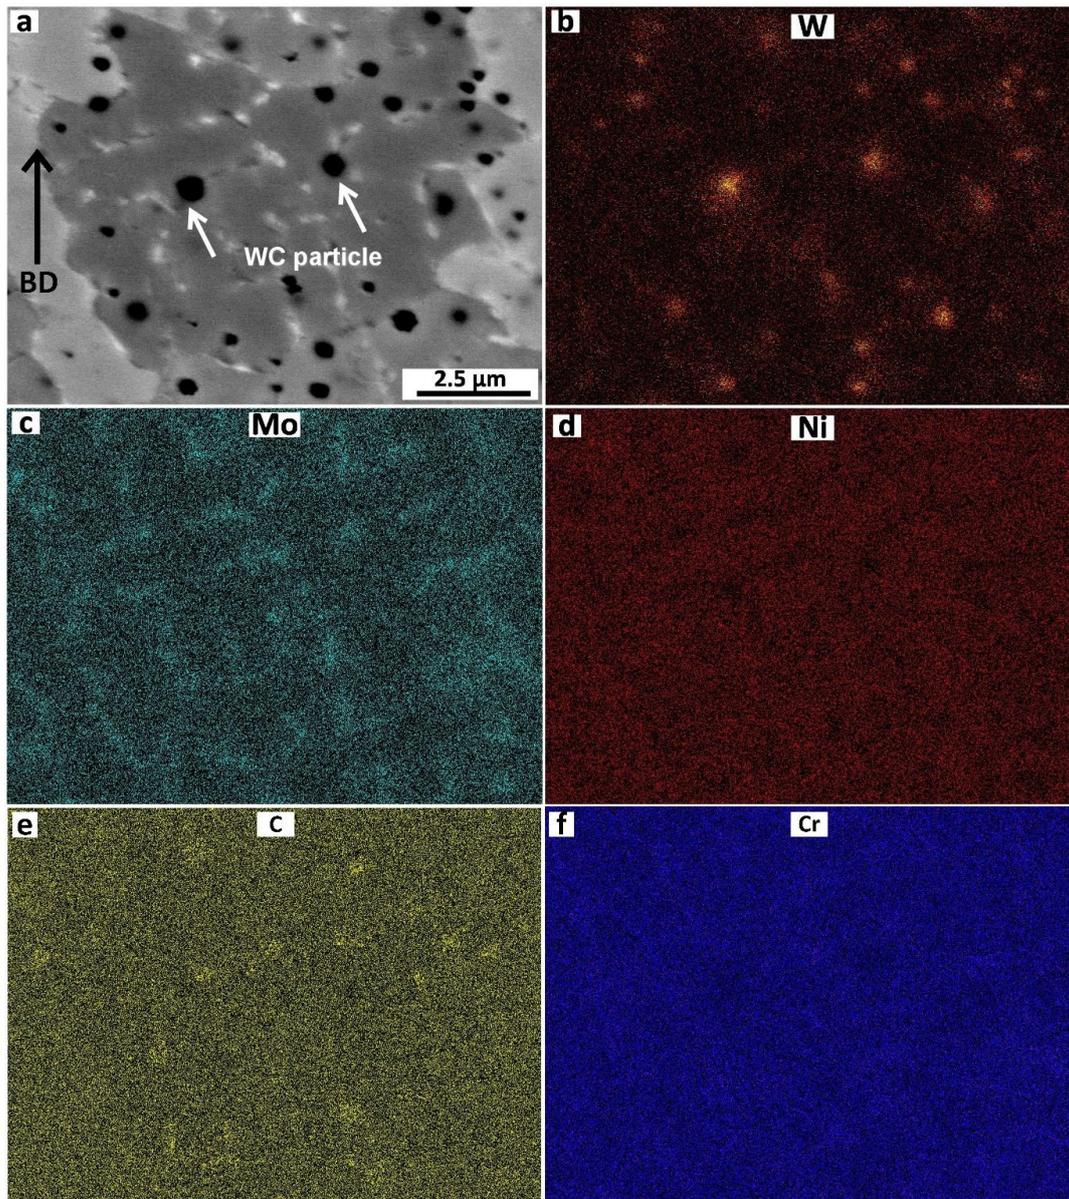


Fig. 6. The uniform distribution of WC particles in HX matrix: (a) high magnification SEM image of the composite; (b)-(f) EDS mapping for the area shown in Fig. 6a.

A high-magnification BSD-SEM micrograph reveals the distribution of WC particles in the HX matrix (Fig. 6a); considering the CTE difference between WC particles and the HX matrix, a higher dislocation density was expected in the as-fabricated composite to enhance the mechanical strength, which will be investigated in the next subsection. The BSD-SEM micrograph also clearly shows that the majority of the WC particles were uniformly distributed in the HX matrix, as confirmed by the EDS mapping analysis (Fig. 6b-f). This may be due to the fact that during the rapid melting and solidification stage, the Marangoni convection in the molten pool could have contributed to break the WC clusters and disperse the fine particles, rather than further agglomerating them together. The Marangoni convection is known to be derived from

1 the molten pool surface's tension gradients; the molten fluid tends to flow from hot
2 areas to relatively cool areas in the molten pool [43][44]. The EDS mapping analysis
3 also reveals that segregation occurred within the LPBF process and the segregated
4 phase was found to be Mo-enrichment around the fine cellular structure (Fig. 6c).
5
6

7 Fig. 7 shows the EBSD micrographs for both pure HX and composite materials.
8 These images are useful for the investigation of the added WC particles in changing
9 the microstructure of HX-WC composites. Both materials offered random grain
10 orientations but the grain size and morphology differed in the two samples after the
11 LPBF process (Fig. 7a/c). In addition, a large number of columnar grains formed in
12 both materials, suggesting that the added WC particles may not be an effective
13 nucleating agent to promote the heterogeneous nucleation and formation of finer
14 grains in the fabricated HX-WC composite. However, the composite exhibited a
15 significant increase in LAGBs compared to the pure HX material on the basis of the
16 EBSD image quality maps (Fig. 7b/d). The LAGBs or subgrain boundaries are those
17 grains with a misorientation less than 10 degrees and are generally composed of an
18 array of dislocations.
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

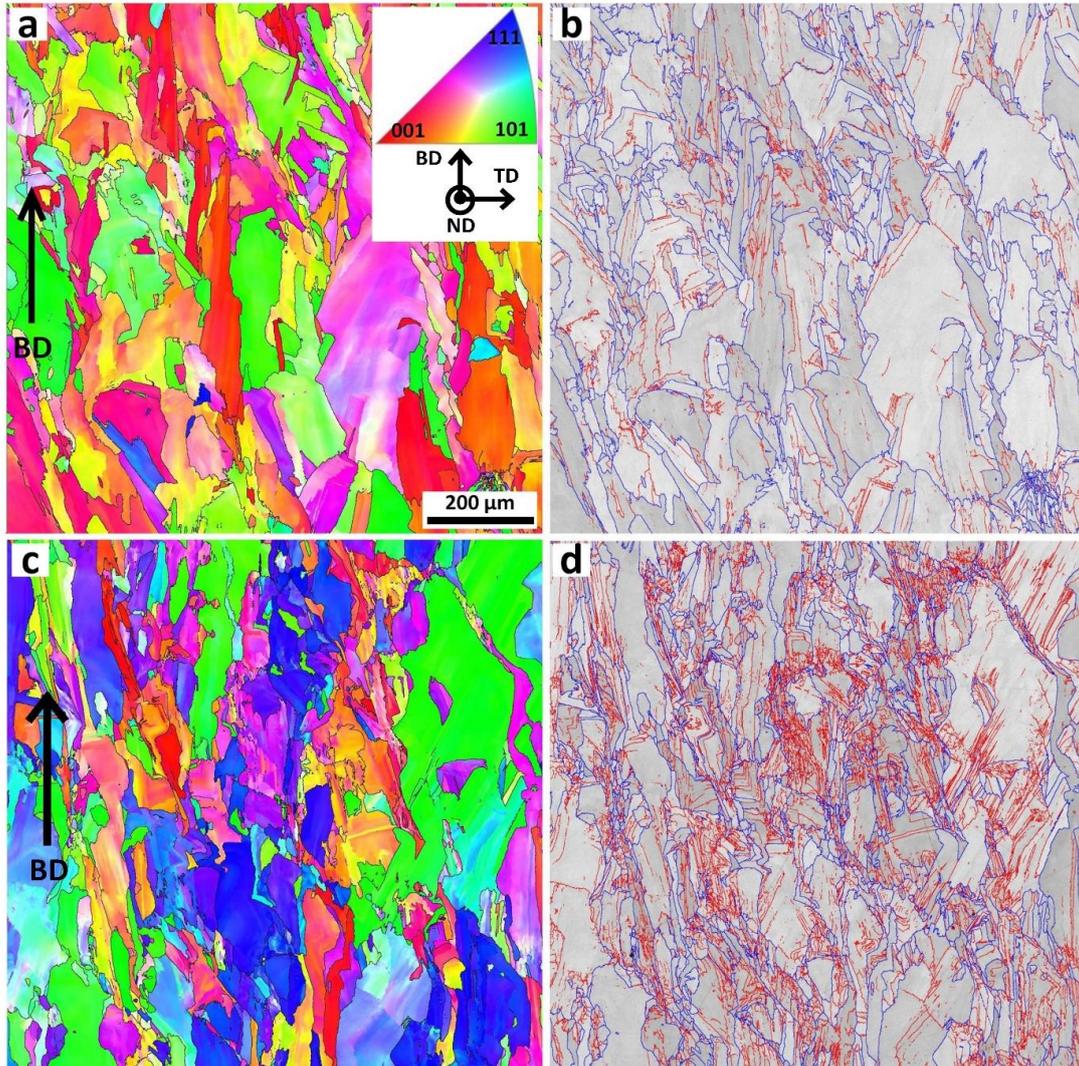



Fig. 7. EBSD images of the fabricated samples: (a) inverse-pole figure (IPF) map of the pure HX; (b) EBSD image quality (IQ) map with high-angle grain boundaries (HAGBs) and low-angle grain boundaries (LAGBs) superimposed for the pure HX; (c) IPF map of the composite; (d) IQ map with HAGBs and LAGBs superimposed for the composite. HAGBs ($>10^\circ$) are coloured blue and LAGBs (2° - 10°) are red.

As mentioned before, the difference in CTE between the HX matrix and WC particles was a possible contributor for the microcracks formation in the fabricated HX-WC composites. On the other hand, such CTE mismatch was the primary contributor to the significant increase in dislocations for the composite. Previous studies have suggested that the contribution of CTE mismatch strengthening is significant in LPBF-fabricated composites because the CTE difference between the matrix and ceramic particles increases with temperature [45][46]. The entanglements of dislocation lines were anticipated to hinder the dislocations' motion and could have enhanced the mechanical strength of the fabricated composite material. It can be anticipated that the

1
2 LPBF-fabricated advanced composites with high-strength and without microcracking
3 defect could be achieved through a careful selection of ceramic reinforcements.
4


5 3.3. Mechanical behaviour

6
7 Fig. 8 shows the tensile test results of both the as-fabricated pure HX and HX-WC
8 composite specimens and their fracture surfaces. The two specimens (hereafter
9 referred to as HX-a and HX-b) were used to obtain the stress-strain curves for pure
10 HX, while HX-WC-a and HX-WC-b were used for the composite material. The tensile
11 performances for both cases were found to be very consistent. For pure HX, the yield
12 strength and elongation were found to be 590 ± 5 MPa and $37 \pm 2\%$, respectively.
13 Compared to pure HX, the composite specimens were found to have a roughly 80
14 MPa increase in yield strength, while no significant reduction was found in elongation;
15 an average elongation value of 32% was determined. The 13% enhancement in yield
16 strength may be explained by the addition of the 1 wt.% sub-micrometre WC particles.
17 It should be noted that the limited number of microcracks that formed in the composite
18 material were not found to have significantly degraded the tensile strength. However,
19 these may reduce the fatigue performance of the LPBF-fabricated composite
20 specimens.
21
22
23
24
25
26
27
28
29
30
31
32
33

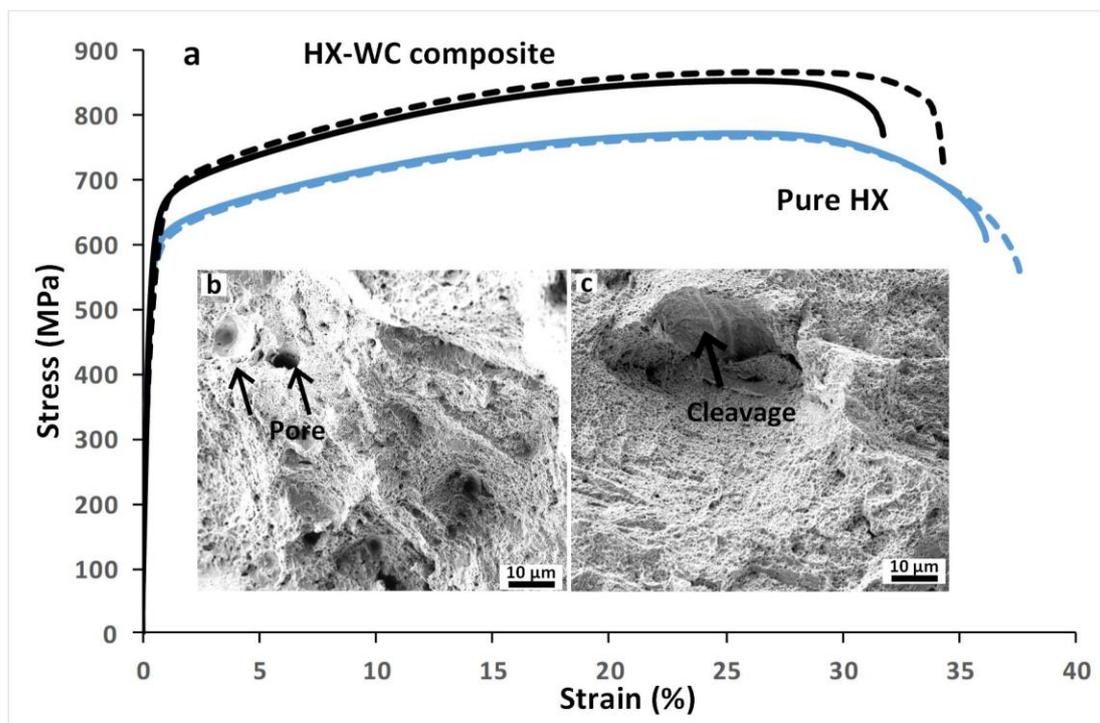

58 **Fig. 8.** Tensile performance of as-fabricated samples: (a) tensile stress-strain curves of as-
59 fabricated pure HX and HX-WC composite; (b) fracture surface for pure HX; (c) fracture
60 surface for the composite.
61
62
63
64
65

1 The fracture surfaces of both pure HX and HX-WC composite samples after tensile
 2 testing are shown in Fig. 8b-c. Both samples exhibited significant necking phenomena
 3 which is consistent with the fact that similar elongation values were found. Compared
 4 to the open pores observed in the as-fabricated samples, both the microcracks and
 5 pores were further opened under uniaxial loading. The limited number of cleavage-like
 6 fracture features and the large number of dimples observed imply a dominance of
 7 ductile fracture behaviour for both materials. This type of fracture behaviour in the
 8 present study was different from that found in the authors' previous study [6], in which
 9 some elongated grains with a dendritic structure were observed in the fracture surface.
 10 This behaviour may be attributable to the difference in the build and loading directions.
 11 In particular, the build direction was parallel to the uniaxial loading direction in the
 12 previous work [6], while the two directions were perpendicular in the present work.
 13 Another possible factor could be the slight difference in alloying composition between
 14 the used HX materials.

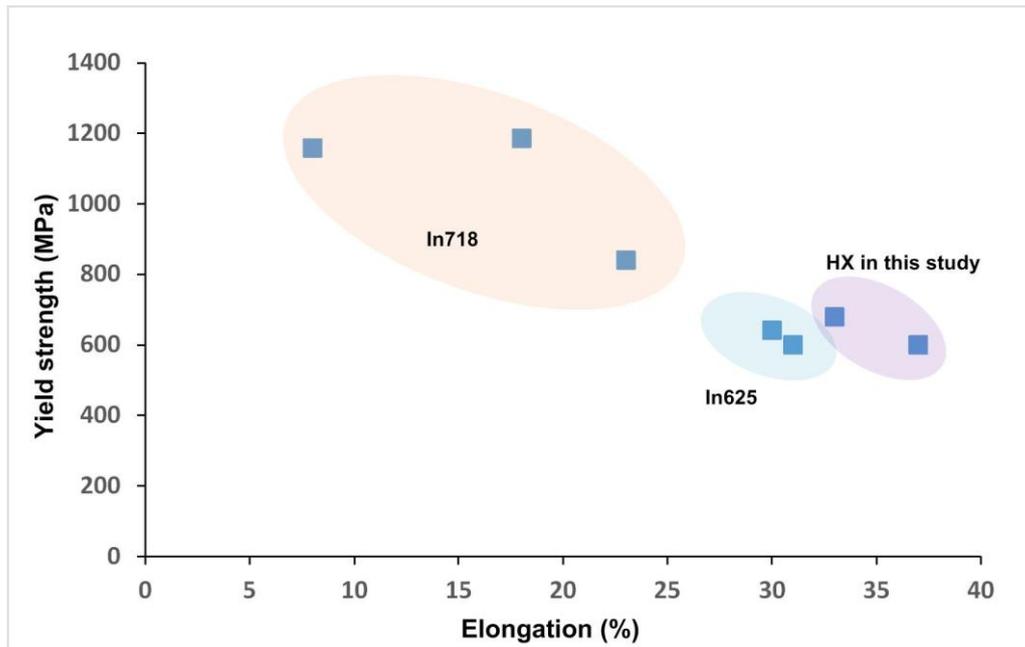

48 **Fig. 9.** 'Yield strength' versus 'elongation to failure' values between HX composites and
 49 typical Inconel alloys [47][48][49][50][16].

50
 51 The 'yield strength' versus 'elongation to failure' values for HX composites
 52 materials reported in the present study compared to the typical Inconel alloys from the
 53 literature are shown in Fig. 9. The LPBF-fabricated Inconel 718 alloy exhibited over
 54 500 MPa increase in yield strength but also witnessed over 15% reduction in
 55 elongation to failure compared to the HX composites. The as-fabricated Inconel 625
 56
 57
 58
 59
 60
 61
 62
 63
 64
 65


1 alloy was found to have comparative yield strength values, but the elongation values
2 were around 5% lower compared to the HX composites. The differences in mechanical
3 performance between HX composites and typical Inconel alloys indicate that the
4 chemical composition plays a significant role in determining the mechanical behaviour
5 of LPBF-fabricated nickel-based superalloys. As mentioned before, the addition of
6 molybdenum in HX alloy enables this material harder, stronger at high temperatures,
7 and also makes it superior for welding applications compared to Inconel alloys.
8
9

10
11
12
13 The underlying microstructure mechanisms between HX and typical Inconel alloys
14 may be attributable to the different precipitation strengthening phases induced by the
15 alloying elements. For instance, the addition of Al and Ti alloying elements in Inconel
16 718 contributes to the formation of gamma prime phase, which significantly enhances
17 the strength of LPBF-fabricated Inconel 718. The added Nb alloying element enables
18 the formation of gamma double prime in Inconel 625 to strengthen this superalloy at
19 lower temperatures (below 700 °C). Compared to Inconel 718 and Inconel 625, HX
20 alloy is a solid-solution strengthening superalloy, which is composed of gamma phase.
21 The addition of sub-micrometre WC ceramic particles could enhance the strength of
22 LPBF-fabricated HX composites through the CTE mismatch strengthening and grain
23 refinement strengthening mechanisms.
24
25
26
27
28
29
30
31
32
33

34 **4. Discussion**

35
36
37 The experimental results of this study demonstrate that the added 1 wt.% sub-
38 micrometre WC particles enabled a roughly 13% improvement in tensile yield strength
39 on the basis of the tensile specimens. The high-speed mixing process was confirmed
40 in this study to be capable of evenly dispersing WC particles on the surface of HX
41 particles. Following the completion of the LPBF process, the majority of the WC
42 particles were observed to be uniformly distributed in the HX-austenite matrix. The
43 underlying microstructure evolution mainly include ceramic reinforcements
44 strengthening and microcracking formation mechanisms induced by ceramic particles
45 agglomeration. Fig. 10a shows a schematic of the potential strengthening mechanism.
46 The primary strengthening mechanism could be the CTE mismatch strengthening that
47 occurs in the composites, where the dislocation density and residual stresses increase
48 due to the mismatch of CTE between the sub-micrometre WC and HX alloy. This
49 strengthening mechanism has been confirmed by our EBSD examination that a much
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 higher dislocation density was detected in the fabricated composite samples
2 compared to the pure HX alloy. However, during the rapid solidification stage in LPBF
3 process, the relatively fine WC particles (150–200 nm) may not act as nucleation sites
4 to promote heterogeneous nucleation and enable the formation of fine grains, because
5 a large number of columnar grains also formed in the as-fabricated composite samples.
6 This may be explained by the high lattice disregistry value between WC and Ni (the
7 matrix in HX alloy) crystals. The degree of potency of the nucleation catalysts could
8 be explained on the basis of the disregistry between the lattice parameters of the
9 substrate and the nucleating phase via the planar crystallographic disregistry theory
10 [51].
11
12
13
14
15
16
17

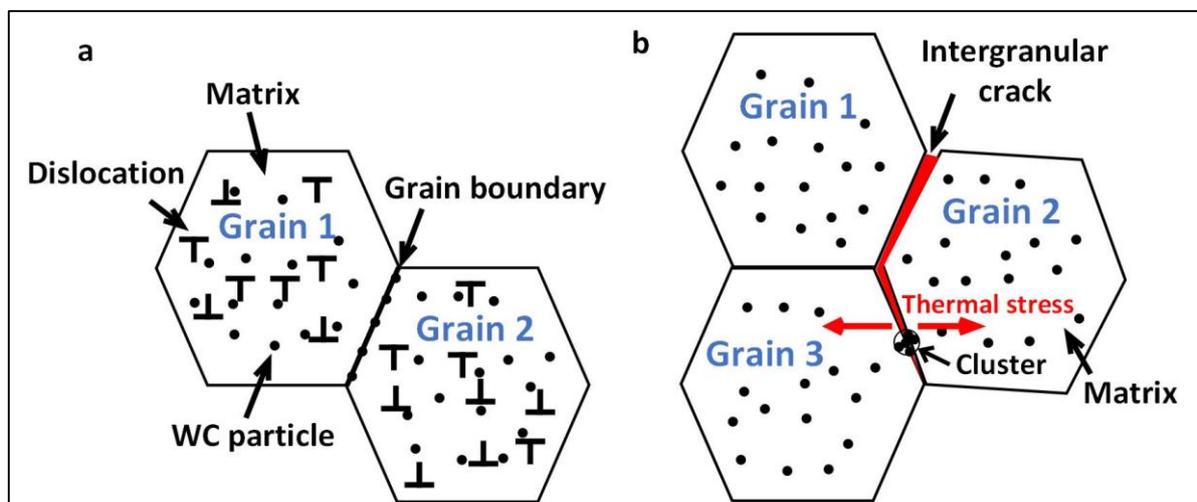

18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36 **Fig. 10.** Schematic of (a) the enhanced dislocation density mechanism and (b) intergranular
37 microcrack formation.
38

39 This study has confirmed that the addition of 1 wt.% WC particles could contribute
40 to a remarkable enhancement in tensile strength of the as-fabricated composite at
41 room temperature. Considering the high-temperature applications of the HX
42 superalloy and the superior hardness, high melting point of WC ceramic particles, the
43 SLM-fabricated HX-WC composite is expected to enable a significant improvement in
44 mechanical performance at high temperatures compared to the pure HX alloy, which
45 will be investigated in future work.
46
47
48
49
50
51

52 The introduction of sub-micrometre WC particles, in addition to enhancing
53 mechanical strength, was also found to result in microcrack formation at the grain
54 boundaries, while those microcracks were not detected in the pure HX after the LPBF
55 process. Fig. 10b shows a possible microcrack formation mechanism in the LPBF-
56 fabricated HX-WC composites. Because of the size of the WC particles (150–200 nm),
57
58
59
60
61
62
63
64
65

1 when a few particles agglomerated on the grain boundaries, those boundaries may
2 tend to become susceptible to hot cracking. Previous studies have reported that Mo-
3 rich and Cr-rich carbides segregate at grain boundaries in the additive manufacturing
4 of HX alloy [52][53]. The Mo-rich carbides were also detected in the fabricated
5 composite sample based on our EDS mapping. The carbides, together with WC
6 clusters, may result in microcrack formation when the accumulated thermal residual
7 stress is sufficient to pull apart two grains, thus forming microcracks. Such microcracks
8 could then propagate along the build direction and grain boundaries and extend to a
9 few layers in length.
10

17 **5. Conclusion**

20 This study has confirmed that the addition of sub-micrometre WC particles to
21 Hastelloy-X (HX) powder could lead to improved tensile strength when manufacturing
22 HX superalloy specimens using the laser powder bed fusion (LPBF) process. This
23 result was derived by investigating for the first time the microstructure and mechanical
24 behaviour of Hastelloy X–1 wt.% WC composite fabricated via LPBF additive
25 manufacturing. This paper has also proposed the possible cracking formation
26 mechanism induced by the added WC particles in the fabricated composites. The
27 following findings were derived from the experimental work.
28
29
30
31
32
33
34
35

- 36 (1) The LPBF-fabricated composite was observed to have a limited number of
37 pores and microcracks, while only pores were detected in the as-fabricated
38 pure HX. The cracks formed in the composite were distributed along the grain
39 boundaries, indicating that they were intergranular cracks. One possible
40 cracking formation mechanism was that the sub-micrometre WC particle
41 clusters, together with the segregated carbides, caused the grain boundaries
42 to be more susceptible to cracking; when the accumulated thermal residual
43 stress is sufficient to pull apart the grains, hot cracking can occur.
44
45
46
47
48
49
- 50 (2) Compared to pure HX, the introduction of 1 wt.% sub-micrometre WC particles
51 contributed to an approximately 13% improvement in tensile yield strength on
52 the basis of tensile specimens but without a significant sacrifice in elongation.
53 The significantly increased dislocations were considered to be the primary
54 contributor to the mechanical performance enhancement in the LPBF-
55 fabricated composite material.
56
57
58
59
60
61
62
63
64
65

1 Future work will study both theoretically and experimentally the microcracking
2 formation and the corresponding elimination for composites manufactured via the
3 LPBF additive manufacturing process. In addition, while this study has only
4 investigated the effects of 1 wt.% sub-micrometre WC particles on the mechanical
5 behaviours of LPBF-fabricated composites, different levels of WC reinforcement will
6 be investigated in future work. It can also be anticipated that the LPBF-fabricated
7 advanced composites with high-strength and without microcracking defect could be
8 achieved through a careful selection of ceramic reinforcements.
9
10
11
12
13
14

15 **Acknowledgements**

16 The lead author gratefully appreciates the financial support of the Qilu Young Scholar
17 Programme (Grant No. 31360082063010), Shandong University, China. The authors
18 also wish to thank ASTUTE 2020, a large-scale research programme, funded by the
19 Welsh European Funding Office through the Welsh Government and the participating
20 HE Institutions.
21
22
23
24
25
26

27 **Conflict of interest**

28 The paper has no conflict of interest in any person or organisation.
29
30
31
32

33 **Data Availability**

34 The raw/processed data required to reproduce these findings cannot be shared at
35 this time as the data also forms part of an ongoing study.
36
37
38
39

40 **References**

- 41 1. Yap CY, Chua CK, Dong ZL, et al (2015) Review of selective laser melting: Materials and
42 applications. *Appl. Phys. Rev.* 2:041101
- 43 2. Lewandowski JJ, Seifi M (2016) Metal Additive Manufacturing: A Review of Mechanical
44 Properties. *Annu Rev Mater Res* 46:151–186. <https://doi.org/10.1146/annurev-matsci-070115-032024>
- 45 3. Han Q, Gu Y, Setchi R, et al (2019) Additive manufacturing of high-strength crack-free Ni-
46 based Hastelloy X superalloy. *Addit Manuf* 30:100919.
47 <https://doi.org/10.1016/j.addma.2019.100919>
- 48 4. Attallah MM, Jennings R, Wang X, Carter LN (2016) Additive manufacturing of Ni-based
49 superalloys: The outstanding issues. *MRS Bull.* 41:758–764
- 50 5. Hinojos A, Mireles J, Reichardt A, et al (2016) Joining of Inconel 718 and 316 Stainless Steel
51 using electron beam melting additive manufacturing technology. *Mater Des* 94:17–27.
52 <https://doi.org/10.1016/j.matdes.2016.01.041>
- 53 6. Han Q, Mertens R, Montero-Sistiaga M, et al (2018) Laser powder bed fusion of Hastelloy X:
54 effects of hot isostatic pressing and the hot cracking mechanism. *Mater Sci Eng A* 732:228–
55 239. <https://doi.org/https://doi.org/10.1016/j.msea.2018.07.008>
56
57
58
59
60
61
62
63
64
65

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
7. Harrison NJ, Todd I, Mumtaz K (2015) Reduction of micro-cracking in nickel superalloys processed by Selective Laser Melting: A fundamental alloy design approach. *Acta Mater* 94:59–68. <https://doi.org/10.1016/j.actamat.2015.04.035>
8. Miracle DB (2005) Metal matrix composites - From science to technological significance. *Compos Sci Technol* 65:2526–2540. <https://doi.org/10.1016/j.compscitech.2005.05.027>
9. Singh N, Singh R, Ahuja IPS, et al (2019) Metal matrix composite from recycled materials by using additive manufacturing assisted investment casting. *Compos Struct* 207:129–135. <https://doi.org/10.1016/j.compstruct.2018.09.072>
10. Han Q, Geng Y, Setchi R, et al (2017) Macro and nanoscale wear behaviour of Al-Al₂O₃ nanocomposites fabricated by selective laser melting. *Compos Part B Eng* 127:26–35. <https://doi.org/10.1016/j.compositesb.2017.06.026>
11. Kang N, Ma W, Heraud L, et al (2018) Selective laser melting of tungsten carbide reinforced maraging steel composite. *Addit Manuf* 22:104–110. <https://doi.org/10.1016/j.addma.2018.04.031>
12. Gu D, Ma J, Chen H, et al (2018) Laser additive manufactured WC reinforced Fe-based composites with gradient reinforcement/matrix interface and enhanced performance. *Compos Struct* 192:387–396. <https://doi.org/10.1016/j.compstruct.2018.03.008>
13. Han Q, Gu Y, Wang L, et al (2020) Effects of TiC content on microstructure and mechanical properties of nickel-based hastelloy X nanocomposites manufactured by selective laser melting. *Mater Sci Eng A* 140008. <https://doi.org/https://doi.org/10.1016/j.msea.2020.140008>
14. Gu D, Zhang H, Dai D, et al (2019) Laser additive manufacturing of nano-TiC reinforced Ni-based nanocomposites with tailored microstructure and performance. *Compos Part B Eng* 163:585–597. <https://doi.org/10.1016/j.compositesb.2018.12.146>
15. Zhang H, Gu D, Xi L, et al (2019) Anisotropic corrosion resistance of TiC reinforced Ni-based composites fabricated by selective laser melting. *J Mater Sci Technol* 35:1128–1136. <https://doi.org/10.1016/j.jmst.2018.12.020>
16. Wang P, Zhang B, Tan CC, et al (2016) Microstructural characteristics and mechanical properties of carbon nanotube reinforced Inconel 625 parts fabricated by selective laser melting. *Mater Des* 112:290–299. <https://doi.org/10.1016/j.matdes.2016.09.080>
17. Rong T, Gu D, Shi Q, et al (2016) Effects of tailored gradient interface on wear properties of WC/Inconel 718 composites using selective laser melting. *Surf Coatings Technol* 307:418–427. <https://doi.org/10.1016/j.surfcoat.2016.09.011>
18. Nguyen QB, Zhu Z, Chua BW, et al (2018) Development of WC-Inconel composites using selective laser melting. *Arch Civ Mech Eng* 184:1410–1420. <https://doi.org/10.1016/j.acme.2018.05.001>
19. Zhao S, Shen X, Yang J, et al (2018) Densification behavior and mechanical properties of nanocrystalline TiC reinforced 316L stainless steel composite parts fabricated by selective laser melting. *Opt Laser Technol* 103:239–250. <https://doi.org/10.1016/j.optlastec.2018.01.005>
20. Wu H, Liu W, He R, et al (2017) Fabrication of dense zirconia-toughened alumina ceramics through a stereolithography-based additive manufacturing. *Ceram Int* 43:968–972. <https://doi.org/10.1016/j.ceramint.2016.10.027>
21. Karthik GM, Panikar S, Ram GDJ, Kottada RS (2017) Additive manufacturing of an aluminum matrix composite reinforced with nanocrystalline high-entropy alloy particles. *Mater Sci Eng A* 679:193–203. <https://doi.org/10.1016/j.msea.2016.10.038>
22. Deshpande PK, Li JH, Lin RY (2006) Infrared processed Cu composites reinforced with WC particles. *Mater Sci Eng A* 429:58–65. <https://doi.org/10.1016/j.msea.2006.04.124>
23. Wang L, Shi JL, Hua Z Le, et al (2001) The influence of addition of WC particles on mechanical properties of alumina-matrix composite. *Mater Lett* 50:179–182. [https://doi.org/10.1016/S0167-577X\(01\)00221-X](https://doi.org/10.1016/S0167-577X(01)00221-X)

- 1
2
3 24. Li X, Xiao Z, Yang C, Qu S (2010) Research on binderless tungsten carbide prepared by spark
4 plasma sintering. *Appl Mech Mater* 37–38:980–984.
5 <https://doi.org/10.4028/www.scientific.net/AMM.37-38.980>
- 6
7 25. Han Q, Gu Y, Soe S, et al (2020) Effect of hot cracking on the mechanical properties of
8 Hastelloy X superalloy fabricated by laser powder bed fusion additive manufacturing. *Opt*
9 *Laser Technol* 124:105984. <https://doi.org/10.1016/j.optlastec.2019.105984>
- 10
11 26. Han Q, Setchi R, Lacan F, et al (2017) Selective laser melting of advanced Al-Al₂O₃
12 nanocomposites: Simulation, microstructure and mechanical properties. *Mater Sci Eng A*
13 698:162–173. <https://doi.org/10.1016/j.msea.2017.05.061>
- 14
15 27. Zhou X, Liu X, Zhang D, et al (2015) Balling phenomena in selective laser melted tungsten. *J*
16 *Mater Process Technol* 222:33–42. <https://doi.org/10.1016/j.jmatprotec.2015.02.032>
- 17
18 28. Liu Y, Zhang J, Yang Y, et al (2017) Study on the influence of process parameters on the
19 clearance feature in non-assembly mechanism manufactured by selective laser melting. *J*
20 *Manuf Process* 27:98–107. <https://doi.org/10.1016/j.jmapro.2017.04.005>
- 21
22 29. Khairallah SA, Anderson AT, Rubenchik A, King WE (2016) Laser powder-bed fusion additive
23 manufacturing: Physics of complex melt flow and formation mechanisms of pores, spatter, and
24 denudation zones. *Acta Mater* 108:36–45
- 25
26 30. Ly S, Rubenchik AM, Khairallah SA, et al (2017) Metal vapor micro-jet controls material
27 redistribution in laser powder bed fusion additive manufacturing. *Sci Rep* 7:4085.
28 <https://doi.org/10.1038/s41598-017-04237-z>
- 29
30 31. Taheri Andani M, Dehghani R, Karamooz-Ravari MR, et al (2017) Spatter formation in
31 selective laser melting process using multi-laser technology. *Mater Des* 131:460–469.
32 <https://doi.org/10.1016/j.matdes.2017.06.040>
- 33
34 32. Heeling T, Cloots M, Wegener K (2017) Melt pool simulation for the evaluation of process
35 parameters in selective laser melting. *Addit Manuf* 14:116–125.
36 <https://doi.org/10.1016/j.addma.2017.02.003>
- 37
38 33. Louvis E, Fox P, Sutcliffe CJ (2011) Selective laser melting of aluminium components. *J Mater*
39 *Process Technol* 211:275–284. <https://doi.org/10.1016/j.jmatprotec.2010.09.019>
- 40
41 34. Aboulkhair NT, Everitt NM, Ashcroft I, Tuck C (2014) Reducing porosity in AlSi10Mg parts
42 processed by selective laser melting. *Addit Manuf* 1–4:77–86.
43 <https://doi.org/10.1016/j.addma.2014.08.001>
- 44
45 35. Leung CLA, Marussi S, Towrie M, et al (2019) The effect of powder oxidation on defect
46 formation in laser additive manufacturing. *Acta Mater* 166:294–305.
47 <https://doi.org/10.1016/j.actamat.2018.12.027>
- 48
49 36. Li XP, Ji G, Chen Z, et al (2017) Selective laser melting of nano-TiB₂decorated AlSi10Mg alloy
50 with high fracture strength and ductility. *Acta Mater* 129:183–193.
51 <https://doi.org/10.1016/j.actamat.2017.02.062>
- 52
53 37. Ang LK, Lau YY, Gilgenbach RM, Spindler HL (1997) Analysis of laser absorption on a rough
54 metal surface. *Appl Phys Lett* 70:696–698. <https://doi.org/10.1063/1.118242>
- 55
56 38. Boley CD, Khairallah SA, Rubenchik AM (2015) Calculation of laser absorption by metal
57 powders in additive manufacturing. *Appl Opt* 54:2477–2482.
58 <https://doi.org/10.1364/ao.54.002477>
- 59
60 39. Ma C, Zhao J, Cao C, et al (2016) Fundamental study on laser interactions with nanoparticles-
61 reinforced metals-part II: Effect of nanoparticles on surface tension, viscosity, and laser
62 melting. *J Manuf Sci Eng Trans ASME* 138:121001. <https://doi.org/10.1115/1.4033446>
- 63
64 40. Nan CW, Birringer R, Clarke DR, Gleiter H (1997) Effective thermal conductivity of particulate
65 composites with interfacial thermal resistance. *J Appl Phys* 81:6692–6699.
<https://doi.org/10.1063/1.365209>
- 66
67 41. Prashanth KG, Eckert J (2017) Formation of metastable cellular microstructures in selective
68 laser melted alloys. *J Alloys Compd* 707:27–34. <https://doi.org/10.1016/j.jallcom.2016.12.209>

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
42. Vora P, Mumtaz K, Todd I, Hopkinson N (2015) AISi12 in-situ alloy formation and residual stress reduction using anchorless selective laser melting. *Addit Manuf* 7:12–19. <https://doi.org/10.1016/j.addma.2015.06.003>
 43. Knapp GL, Mukherjee T, Zuback JS, et al (2017) Building blocks for a digital twin of additive manufacturing. *Acta Mater* 135:390–399. <https://doi.org/10.1016/j.actamat.2017.06.039>
 44. Aucott L, Dong H, Mirihanage W, et al (2018) Revealing internal flow behaviour in arc welding and additive manufacturing of metals. *Nat Commun* 9:5414. <https://doi.org/10.1038/s41467-018-07900-9>
 45. Sanaty-Zadeh A (2012) Comparison between current models for the strength of particulate-reinforced metal matrix nanocomposites with emphasis on consideration of Hall-Petch effect. *Mater Sci Eng A* 531:112–118. <https://doi.org/10.1016/j.msea.2011.10.043>
 46. Yu WH, Sing SL, Chua CK, et al (2019) Particle-reinforced metal matrix nanocomposites fabricated by selective laser melting: A state of the art review. *Prog Mater Sci* 104:330–379. <https://doi.org/10.1016/j.pmatsci.2019.04.006>
 47. Zhang D, Niu W, Cao X, Liu Z (2015) Effect of standard heat treatment on the microstructure and mechanical properties of selective laser melting manufactured Inconel 718 superalloy. *Mater Sci Eng A* 644:32–40. <https://doi.org/10.1016/j.msea.2015.06.021>
 48. Chlebus E, Gruber K, Kuźnicka B, et al (2015) Effect of heat treatment on the microstructure and mechanical properties of Inconel 718 processed by selective laser melting. *Mater Sci Eng A* 639:647–655. <https://doi.org/10.1016/j.msea.2015.05.035>
 49. Trosch T, Strößner J, Völkl R, Glatzel U (2016) Microstructure and mechanical properties of selective laser melted Inconel 718 compared to forging and casting. *Mater Lett* 164:428–431. <https://doi.org/10.1016/j.matlet.2015.10.136>
 50. Salarian M, Asgari H, Vlasea M (2020) Pore space characteristics and corresponding effect on tensile properties of Inconel 625 fabricated via laser powder bed fusion. *Mater Sci Eng A* 769:138525. <https://doi.org/10.1016/j.msea.2019.138525>
 51. Bramfitt BL (1970) The effect of carbide and nitride additions on the heterogeneous nucleation behavior of liquid iron. *Metall Trans* 1:1987–1995. <https://doi.org/10.1007/BF02642799>
 52. Marchese G, Bassini E, Aversa A, et al (2019) Microstructural evolution of post-processed Hastelloy X alloy fabricated by laser powder bed fusion. *Materials (Basel)* 12:486. <https://doi.org/10.3390/ma12030486>
 53. Jinoop AN, Denny J, Paul CP, et al (2019) Effect of post heat-treatment on the microstructure and mechanical properties of Hastelloy-X structures manufactured by laser based Directed Energy Deposition. *J Alloys Compd* 797:399–412. <https://doi.org/10.1016/j.jallcom.2019.05.050>